

AD-A044 669

FOREIGN TECHNOLOGY DIV WRIGHT-PATTERSON AFB OHIO  
RESISTANCE OF DIELECTRIC COATINGS OF LEAD OXIDE AND CRYOLITE TO--ETC(U)  
NOV 76 N L KRAMARENKO, Y V NABOYKIN  
FTD-ID(RS)I-1600-76

F/G 20/5

UNCLASSIFIED

NL

1 OF 1  
ADA  
044669



END  
DATE  
FILMED  
10-77  
DDC

AD-A044669

FTD-ID(RS)I-1600-76

①


## FOREIGN TECHNOLOGY DIVISION



RESISTANCE OF DIELECTRIC COATINGS OF LEAD OXIDE  
AND CRYOLITE TO LASER RADIATION


by

N. L. Kramarenko, Yu. V. Naboykin, Yu. A. Tiunov

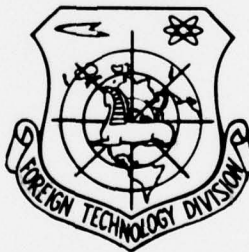

DDC  
SEP 25 1977  
RECEIVED

Approved for public release;  
distribution unlimited.



## EDITED TRANSLATION

FTD-ID(RS)I-1600-76

16 November 1976

RESISTANCE OF DIELECTRIC COATINGS OF LEAD OXIDE  
AND CRYOLITE TO LASER RADIATION

By: N. L. Kramarenko, Yu. V. Naboykin, Yu. A.  
Tiunov

English pages: 5

Source: Kvantovaya Elektronika Trudy Respublikanskogo  
Seminara, Izd-vo "Naukova Dumka," Kiev, 1969,  
Nr 3, PP. 311-313.

Country of origin: USSR

Translated by: Robert Potts

Requester: FTD/PDRR

Approved for public release; distribution unlimited.

ACQUISITION IN	
NTIS	Write Section <input checked="" type="checkbox"/>
DDC	Buy Section <input type="checkbox"/>
UNCLASSIFIED	<input type="checkbox"/>
JUSTIFICATION	
BY _____	
DATE/INITIALS/DATE	
SOL. INFO. WORK SPECIAL	
A	

THIS TRANSLATION IS A RENDITION OF THE ORIGINAL FOREIGN TEXT WITHOUT ANY ANALYTICAL OR EDITORIAL COMMENT. STATEMENTS OR THEORIES ADVOCATED OR IMPLIED ARE THOSE OF THE SOURCE AND DO NOT NECESSARILY REFLECT THE POSITION OR OPINION OF THE FOREIGN TECHNOLOGY DIVISION.

PREPARED BY:

TRANSLATION DIVISION  
FOREIGN TECHNOLOGY DIVISION  
WP-AFB, OHIO.

FTD ID(RS)I-1600-76

Date 16 Nov 19 76

# U. S. BOARD ON GEOGRAPHIC NAMES transliteration SYSTEM

Block	Italic	Transliteration	Block	Italic	Transliteration
А а	<b>А а</b>	A, a	Р р	<b>Р р</b>	R, r
Б б	<b>Б б</b>	B, b	С с	<b>С с</b>	S, s
В в	<b>В в</b>	V, v	Т т	<b>Т т</b>	T, t
Г г	<b>Г г</b>	G, g	У у	<b>У у</b>	U, u
Д д	<b>Д д</b>	D, d	Ф ф	<b>Ф ф</b>	F, f
Е е	<b>Е е</b>	Ye, ye; E, e*	Х х	<b>Х х</b>	Kh, kh
Ж ж	<b>Ж ж</b>	Zh, zh	Ц ц	<b>Ц ц</b>	Ts, ts
З з	<b>З з</b>	Z, z	Ч ч	<b>Ч ч</b>	Ch, ch
И и	<b>И и</b>	I, i	Ш ш	<b>Ш ш</b>	Sh, sh
Й й	<b>Й й</b>	Y, y	Щ щ	<b>Щ щ</b>	Shch, shch
К к	<b>К к</b>	K, k	Ъ ъ	<b>Ъ ъ</b>	"
Л л	<b>Л л</b>	L, l	Ы ы	<b>Ы ы</b>	Y, y
М м	<b>М м</b>	M, m	Ь ь	<b>Ь ь</b>	'
Н н	<b>Н н</b>	N, n	Э э	<b>Э э</b>	E, e
О о	<b>О о</b>	O, o	Ю ю	<b>Ю ю</b>	Yu, yu
П п	<b>П п</b>	P, p	Я я	<b>Я я</b>	Ya, ya

\*ye initially, after vowels, and after ъ, ь; e elsewhere.  
 When written as ё in Russian, transliterate as yë or ë.  
 The use of diacritical marks is preferred, but such marks may be omitted when expediency dictates.

## GREEK ALPHABET

Alpha	A	α	α	Nu	N	ν
Beta	B	β		Xi	Ξ	ξ
Gamma	Γ	γ		Omicron	Ο	ο
Delta	Δ	δ		Pi	Π	π
Epsilon	E	ε	ε	Rho	Ρ	ρ ϑ
Zeta	Z	ζ		Sigma	Σ	σ ς
Eta	H	η		Tau	Τ	τ
Theta	Θ	θ	θ	Upsilon	Υ	υ
Iota	I	ι		Phi	Φ	φ φ
Kappa	K	κ	κ x	Chi	Χ	χ
Lambda	Λ	λ		Psi	Ψ	ψ
Mu	M	μ		Omega	Ω	ω

# RUSSIAN AND ENGLISH TRIGONOMETRIC FUNCTIONS

Russian	English
sin	sin
cos	cos
tg	tan
ctg	cot
sec	sec
cosec	csc
sh	sinh
ch	cosh
th	tanh
cth	coth
sch	sech
csch	csch
arc sin	$\sin^{-1}$
arc cos	$\cos^{-1}$
arc tg	$\tan^{-1}$
arc ctg	$\cot^{-1}$
arc sec	$\sec^{-1}$
arc cosec	$\csc^{-1}$
arc sh	$\sinh^{-1}$
arc ch	$\cosh^{-1}$
arc th	$\tanh^{-1}$
arc cth	$\coth^{-1}$
arc sch	$\operatorname{sech}^{-1}$
arc csch	$\operatorname{csch}^{-1}$
<hr/>	
rot	curl
lg	log

## GRAPHICS DISCLAIMER

All figures, graphics, tables, equations, etc. merged into this translation were extracted from the best quality copy available.

RESISTANCE OF DIELECTRIC COATINGS OF LEAD OXIDE  
AND CRYOLITE TO LASER RADIATION

N. L. Kramarenko, Yu. V. Naboykin, Yu. A. Tiunov

In connection with the continuous development of investigations in the field of lasers, the need increases for dielectric coatings serving as resonator mirrors. The main requirements, which are imposed on such coatings, are high reflecting properties and resistance to laser radiation, especially with high energy densities.

Existing mirrors on a base of zinc sulfide and various fluorides possess sufficiently high strength and high coefficients of reflectivity. However, substances are known for which the refractive indices are higher than for zinc sulfide. This makes it possible to produce mirrors from a smaller number of layers with the same parameters than for mirrors from zinc sulfide. Such substances include lead oxide.


In this article by means of the application of alternating layers of lead oxide and cryolite in a vacuum we obtained multilayer mirrors, which were applied as reflectors in a laser resonator. Some optical properties of such multilayers are investigated in [1-3]. In our work we discussed the results of investigation of the resistance of these coatings to ruby laser radiation depending on the method of their preparation and the number of deposited layers. Multilayer coatings of lead oxide and cryolite were obtained by



means of vaporization of substances in an ordinary vacuum installation [4] with a rectifier, with which it is possible to regulate the degree of vacuum under the cover. Regulation is necessary since the lead oxide layers are applied with  $p \sim 3 \cdot 10^{-4}$  torr [2], and cryolite layers with  $p \sim 1 \cdot 10^{-5}$  torr. The rate of pulverization of lead oxide with such a vacuum is approximately  $500 \text{ Å/min.}$  The refractive index of PbO layers highly depends on the temperature of the backing. So, with temperature  $20^\circ\text{C}$  the refractive index for  $\lambda = 5780 \text{ Å}$  is equal to 2.55, and with temperature  $200^\circ\text{C}$   $n = 2.71$ . The relationship of reflectivity of the lead oxide layers to the temperature of the backing is studied in detail in [3]. We applied the lead oxide layers to the backing at temperature 20 and  $200^\circ\text{C}$ . Multilayer coatings from lead oxide and cryolite, applied at different temperatures of backing, for lead oxide were tested for durability against ruby laser radiation, and the coefficients of reflectivity were measured on an instrument, made according to the Dufour scheme [4].

In literature there are practically no data on the resistance of laser reflectors to the action of coherent radiation. In [5] are described the strength characteristics of multilayers of zinc sulfide and magnesium fluoride. As our investigations have shown, it is difficult to systematically evaluate the strength of coatings against radiation because of their surface irregularity and the necessity of using focused laser radiation on some section of the surface. The strength of multilayer coatings was studied by the following method. A ruby laser beam (figure) with maximum output energy  $\sim 4 \text{ J}$ , operating in free-running mode,

was focused with lens  $\mathcal{L}_1$  on the inlet opening of IF-68 vacuum calorimeter.

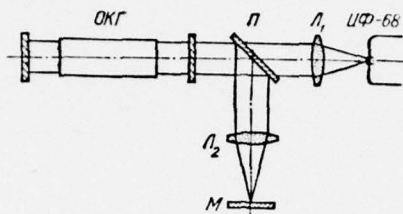

The other part of the beam ( $\sim 20\%$ ) was separated with the aid of beam splitting plate  $\Pi$  and was focused with lens  $\mathcal{L}_2$  on multilayer M. For determining the quantity of incident energy on the sample the energy was measured with plate  $\Pi$  and without it. Such a scheme of installation gave the possibility of precisely recording the energy of breakdown of the multilayer. A criterion of disturbance of the strength of coating was the appearance of a noticeable spot on its surface. The area of the spot was determined by the following method: it was photographed under a microscope, and then its area was found by weighing the photograph of the contour cut from paper. Thus we determined the maximum density of energy at which the coating was destroyed. We started to irradiate the microlayer with lower energy than the breakdown energy, and gradually brought it to a limiting value, at which the spot appeared on the surface.

(1)	(2)	(3)	(2)	(3)
Число слоев	Коэффициент отражения, %	W пред- ож/см <sup>2</sup> , при t <sub>под</sub> = 20° C	Коэффициент отражения, %	W пред- ож/см <sup>2</sup> , при t <sub>под</sub> = 200° C
1	40	680	44	2100
5	86	500	90	1400
7	95	360	97	1300
9	97	320	99	640



Table key: a. number of layers, b. coefficient of reflectivity, %, c.  $W_{\text{limit}}$ , J/cm<sup>2</sup>, with  $t_{\text{back}}=200^{\circ}\text{C}$ .

The experimental values of limiting energy densities, at which the coating was destroyed, are provided in the table. These data correspond to values of the breakdown energy, averaged along the surface of the microlayer coating. From the table we see that the strength of multilayer coatings is increased with decrease of the number of layers: so, a ten-layer has density of breakdown energy 320 J/cm<sup>2</sup> and a one-layer - 680 J/cm<sup>2</sup>. Multilayers, for which the temperature of backing with the application of lead oxide was 200°C, have a sharper relationship of limiting energy density to the number of layers: for ten-layer the limiting energy density is 640 J/cm<sup>2</sup>, and one-layer - 2100 J/cm<sup>2</sup>.

Single-layer coatings, for which lead oxide is applied on a hot backing at  $t=200^{\circ}\text{C}$ , turned out to be stronger. Heating of the backing, on the one hand, increases the adhesion of the first layer with the backing, and on the other hand decreases the absorption of the multilayer and increases its reflectivity, which leads to the increase of strength.

The energy densities, which multilayer coatings of lead oxide and cryolite withstand, are lower than the densities provided in [5] for multilayers from zinc sulfide and magnesium fluoride. This is apparently connected with the low melting temperature of lead oxide ( $t=888^{\circ}\text{C}$ ) in comparison with the melting

point of zinc sulfide. However, increase of the density of coatings, which is observed with heating of the backing to 200°C, permits having confidence that treatment of the backing can improve the resistance of lead oxide and cryolite coatings to laser radiation.

#### BIBLIOGRAPHY

1. Набойкин Ю. В., Крамаренко И. Л.— ПТЭ, 1965, 2, 189
2. Слархам Р. В.— J. Sci. Instrum., 1962, 39, 596.
3. Набойкин Ю. В., Крамаренко И. Л., Акопов В. М.— Журнал прикладной спектроскопии, 1966, 5, 2, 153.
4. Толанский С. Спектроскопия высокой разрешающей силы. ИЛ. М., 1955.
5. Бонч-Бруевич А. М., Имас Я. А.— Журнал прикладной спектроскопии, 1964, 1, 3, 265.

Physicotechnical Institute of Low Temperatures of AN USSR

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER FTD-ID(RS)I-1600-76	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) RESISTANCE OF DIELECTRIC COATINGS OF LEAD OXIDE AND CRYOLITE TO LASER RADIATION		5. TYPE OF REPORT & PERIOD COVERED Translation
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) N. L. Kramarenko, Yu. V. Naboykin, Yu. A. Tiunov		8. CONTRACT OR GRANT NUMBER(s)
9. PERFORMING ORGANIZATION NAME AND ADDRESS Foreign Technology Division Air Force Systems Command U. S. Air Force		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS
11. CONTROLLING OFFICE NAME AND ADDRESS		12. REPORT DATE 1969
		13. NUMBER OF PAGES 5
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		15. SECURITY CLASS. (of this report) UNCLASSIFIED
		15a. DECLASSIFICATION DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number)		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number)  09		

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 65 IS OBSOLETE

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

# DISTRIBUTION LIST

## DISTRIBUTION DIRECT TO RECIPIENT

ORGANIZATION	MICROFICHE	ORGANIZATION	MICROFICHE
A205 DMATC	1	E053 AF/INAKA	1
A210 DMAAC	2	E017 AF/RDQLR-W	1
B344 DIA/DS-4C	8	E404 AEDC	1
C043 USAMIIA	1	E408 AFWL	1
C509 BALLISTIC RES LABS	1	E410 ADTC	1
C510 AIR MOBILITY R&D	1	E413 ESD	2
LAB/FIO		FTD	
C513 PICATINNY ARSENAL	1	CCN	1
C535 AVIATION SYS COMD	1	ETID	3
C557 USAIIC	1	NIA/PHS	1
C591 PSTC	5	NICD	5
C619 MIA REDSTONE	1		
D008 NISC	1		
H300 USAICE (USAREUR)	1		
P005 ERDA	2		
P055 CIA/CRS/ADD/SD	1		
NAVORDSTA (50L)	1		
NAWPNSCEN (Code 121)	1		
NASA/KSI	1		
544 IES/RDPO	1		
AFIT/LD	1		